



**HAL**  
open science

## Narcissistic Self-Sorting of n-Acene Nano-Ribbons yielding Energy-Transfer and Electroluminescence at p-n Junctions

Philip Schäfer, Christiaan de Vet, Leire Gartzia-Rivero, Guillaume Raffy, Min-Tzu Kao, Christian Schäfer, Laura J Romasanta, Bertrand Pavageau, Yu-Tang Tsai, Lionel Hirsch, et al.

► **To cite this version:**

Philip Schäfer, Christiaan de Vet, Leire Gartzia-Rivero, Guillaume Raffy, Min-Tzu Kao, et al.. Narcissistic Self-Sorting of n-Acene Nano-Ribbons yielding Energy-Transfer and Electroluminescence at p-n Junctions. *Nanoscale*, 2022, 14 (25), pp.8951-8958. 10.1039/D2NR01017H . hal-03853690

**HAL Id: hal-03853690**

**<https://hal.archives-ouvertes.fr/hal-03853690>**

Submitted on 15 Nov 2022

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

## Narcissistic Self-Sorting of *n*-Acene Nano-Ribbons yielding Energy-Transfer and Electroluminescence at p-n Junctions

Philip Schäfer,<sup>a</sup> Christiaan de Vet,<sup>a</sup> Leire Gartzia-Rivero,<sup>a,b</sup> Guillaume Raffy,<sup>a</sup> Min-Tzu Kao,<sup>a</sup> Christian Schäfer,<sup>a</sup> Laura J. Romasanta,<sup>c</sup> Bertrand Pavageau,<sup>c</sup> Yu-Tang Tsai,<sup>a,d</sup> Lionel Hirsch,<sup>d</sup> Dario M. Bassani,<sup>a</sup> André Del Guerzo<sup>a\*</sup>

Received 00th January 20xx,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

The 2,3-didecyloxy-derivative of an n-type anthracene (**n-BG**) and a p-type tetracene (**p-R**) have been synthesized and their self-assembly into nano-ribbons studied. Hyperspectral fluorescence imaging revealed their narcissistic self-sorting, leading to separated nanoribbons emitting with very different colors (blue or green for **n-BG**, depending on the growth solvent, and red for **p-R**). It is unique that the usual origins of self-sorting, such as specific H-bonding, different growth kinetics, or incompatible steric hindrance can be ruled out. Hence, the narcissistic behaviour is herein proposed to originate from a so far unconsidered cause: the discrepancy between the quadrupolar character of **n-BG** and dipolar character of **p-R**. At the p-n-junctions of these nanoribbons, inter-ribbon FRET and electro-luminescence switch-on were observed by fluorescence microscopy.

### Introduction

Orthogonally self-assembled systems,<sup>1</sup> sometimes self-sorted, are essential to generate complexity and function in biological systems, and have therefore been transposed to biomimetics,<sup>2–5</sup> tissue-engineering,<sup>6–8</sup> as well as optoelectronics.<sup>9–14</sup> van Esch defined orthogonal self-assembly as the independent formation of two different supramolecular structures, each with their own characteristics that coexist within a single system;<sup>15</sup> Whitesides initially described it as an individual but simultaneous self-assembly.<sup>16</sup> Orthogonal self-assembly is very important to preserve integrity of multiple components and achieve synergistic property enhancement or introduction of new behavior, whether macroscopically or at interfaces. Self-sorting is certainly one of the most appealing mechanism to achieve this, as it also infers ‘one-pot’ processing. It can occur as a rarer narcissistic self-sorting, in which identical molecules assemble separately from other components present, or a social self-sorting, which involves specific blending of components.<sup>17</sup> The use of orthogonal binding motives has been considered of prime importance to achieve narcissistic self-sorting.<sup>18</sup> In many cases, multiple H-bonding sites are introduced and tuned to differentiate the binding patterns<sup>19,20</sup> of the different components, or very different constituents such as lipids and peptides are used.<sup>21,22</sup> Some of these ‘molecular codes’, as classified by

Würthner,<sup>23</sup> can be readily distinguished in the molecular structures. However, in the less evident cases, for example a rare case of narcissistic self-sorting without H-bonds of perylene derivatives, only the contribution of steric hindrance could be proposed as origin of the sorting.<sup>24</sup>

The focus on self-sorted heterojunctions is also quite rare, whether localized or co-axial,<sup>25</sup> and to the best of our knowledge always involve H-bonding systems. Shinkai and coworkers demonstrated the formation of a dual network of p- and n-type semiconductor-based nanofibers due to differentiated growth kinetics, leading to small amounts of hetero-junctions and resulting photo-current in a device.<sup>26</sup> From the few comparable studies, some common features appear: (i) the dual network formation is based on differentiated assembly kinetics<sup>27</sup> (due to different thermodynamic stabilities or  $pK_a$ <sup>28</sup>); (ii) H-bonds are of prime importance in the self-recognition; (iii) the functional polyaromatic unit is surrounded by rather medium-to-large bulky groups (cholesteric units,<sup>26</sup> amido-trioctylxyphenyl units,<sup>19</sup> peptides<sup>29</sup>). The latter bulky substituents could however be detrimental in optoelectronics.

In this work, quite compact polyaromatic, H-bond-free fluorescent *n*-acene derivatives are used to form narcissistic self-sorted p- and n-type self-assemblies with generation of electroluminescence at interfaces. Such a system would be expected to be very sensitive to incomplete self-sorting, and necessitates favourable interfacial interactions. On a fundamental level, this work contributes unravelling mechanisms that lead to a remarkable narcissistic self-sorting of relatively similar polyaromatic molecules having the same side chains, without forming H-bonds. In addition, in this work hyper-spectral confocal fluorescence microscopy (HS-CFM), rarely used in similar contexts,<sup>30</sup> is revealed as an efficient tool to image multi-component materials and interfaces therein, whereas these are commonly considered difficult to characterize.<sup>31</sup>

<sup>a</sup> Univ. Bordeaux, CNRS, Bordeaux INP, Institut des Sciences Moléculaires UMR 5255, 351 Cours de la Libération, F-33400 Talence (France); e-mail: andre.del-guerzo@u-bordeaux.fr

<sup>b</sup> Department of Physical Chemistry, University of the Basque Country (UPV/EHU), Apartado 644, 48080 Bilbao (Spain)

<sup>c</sup> CNRS, Solvay, Univ. Bordeaux, LOF, UMR 5258, 178 Avenue du Dr. Albert Schweitzer, F-33600 Pessac (France)


<sup>d</sup> Univ. Bordeaux, CNRS, Bordeaux INP, ENSCPB, IMS, CNRS UMR 5218, F-33600 Pessac (France)

Electronic Supplementary Information (ESI) available: [synthesis, spectroscopy, microscopy, calculations, methods]. See DOI: 10.1039/x0xx00000x

## Results and discussion

### Self-Sorting

Previous work on *n*-acenes has shown that 2,3-dialkoxy substitution promotes formation of anisotropic self-assemblies such as nanofibers of 2,3-didicyloxyanthracene (DDOA)<sup>32,33</sup> or nanoribbons of 9,10-diphenyl-2,3-dihexadecyloxyanthracene<sup>34</sup> in alcohols and DMSO. If compared, ribbons are wider than fibres with a higher width/height aspect ratio, which in contrast tend to form twisted bundles, branching and gels. Ribbons are nevertheless thinner than most crystals. The alkoxy chains have been shown to alter the solubility, and also promote a sheet-like packing of the molecules alternating aromatic cores and alkyl chains in nanoribbons.<sup>34</sup> Therefore, 9,10-dicyano-2,3-didicyloxyanthracene (herein called **n-BG** 'n-type-blue/green') was prepared as an electro-deficient n-type self-assembling derivative, whereas 2,3-didicyloxy-6,11-diphenyl-5,12-diphenylethynyltetracene (**p-R** 'p-type-red') can be expected to act as a p-type derivative owing to the tetracene core (Scheme 1, Figure 1a). The synthesis of **n-BG** is based on the 9,10-bromination of previously described DDOA<sup>32</sup> and subsequent substitution with cyano groups. **p-R** is obtained from 2,3-didicyloxy-6,11-diphenyltetracene-5,12-dione similar to previously described procedures<sup>35,36</sup> (Scheme 1 and Supplementary Information).

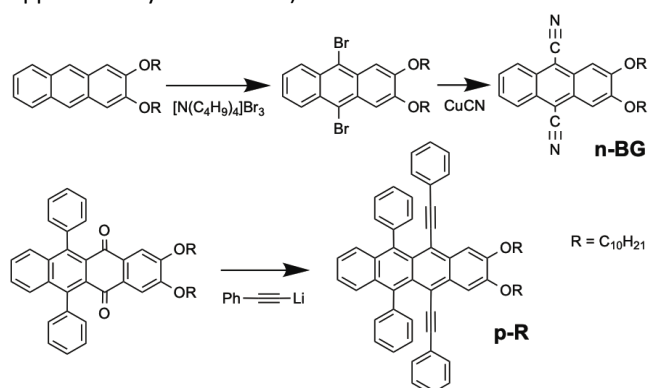


**Scheme 1:** Final steps of the syntheses of **n-BG** and **p-R**.

**Table 1:** Photophysical properties of **n-BG** and **p-R** in solution (sol,  $1.0 \times 10^{-5}$  M) and nanoribbons (NR): quantum yield ( $\Phi_{em}$ ), lifetime ( $\tau$ ), calculated radiative ( $k_r$ ) and non-radiative constants ( $k_{nr}$ ).  $\Phi_{em} = k_r \tau = k_r / (k_r + k_{nr})$ . See also Tables S1, S2.

	$\lambda_{em} \backslash \text{nm}$	$\Phi_{em}$	$\tau \backslash \text{ns}$	$k_r \backslash 10^7 \text{ s}^{-1}$	$k_{nr} \backslash 10^7 \text{ s}^{-1}$
<b>n-BG</b> <sup>a</sup> /sol	435	0.32	6.0	5.3	11.4
<b>n-BG</b> <sup>b</sup> /sol	462	0.26	6.2	3.8 <sup>b</sup>	12.3 <sup>b</sup>
<b>n-BG</b> <sup>c</sup> /NR	545	~0.26	23.6	~1	~3
<b>p-R</b> <sup>d</sup> /sol	603/650	0.73	8.3	8.8	3.2
<b>p-R</b> <sup>e</sup> /NR	620/669	e	0.9	e	e

a: cyclohexane; b: acetone ( $k_r$  calculated for longest  $\tau$ , a second lifetime of 2.5 ns contributes for 8% of the emission); c:  $\lambda_{em}$  and  $\tau$  in mixed ribbons in *n*-butanol,  $\Phi_{em}$  of **n-BG** NR in DCM/butanol ( $\lambda_{em}$ =480 nm),  $k_r$  and  $k_{nr}$  estimated by combining all data; d: toluene; e: could not be determined with accuracy (see Experimental).


Spectroscopic studies in solution show that the anthracene **n-BG** emits blue light from a  $\pi$ - $\pi^*$  transition in apolar cyclohexane solvent (Table 1; Tables S1, S2 and Figure S3 in S.I.). In the polar solvent acetone the emission becomes unstructured and shifted to cyan, and is attributed to an intramolecular charge-transfer ICT state with an excited state dipole of 14 D, as determined by

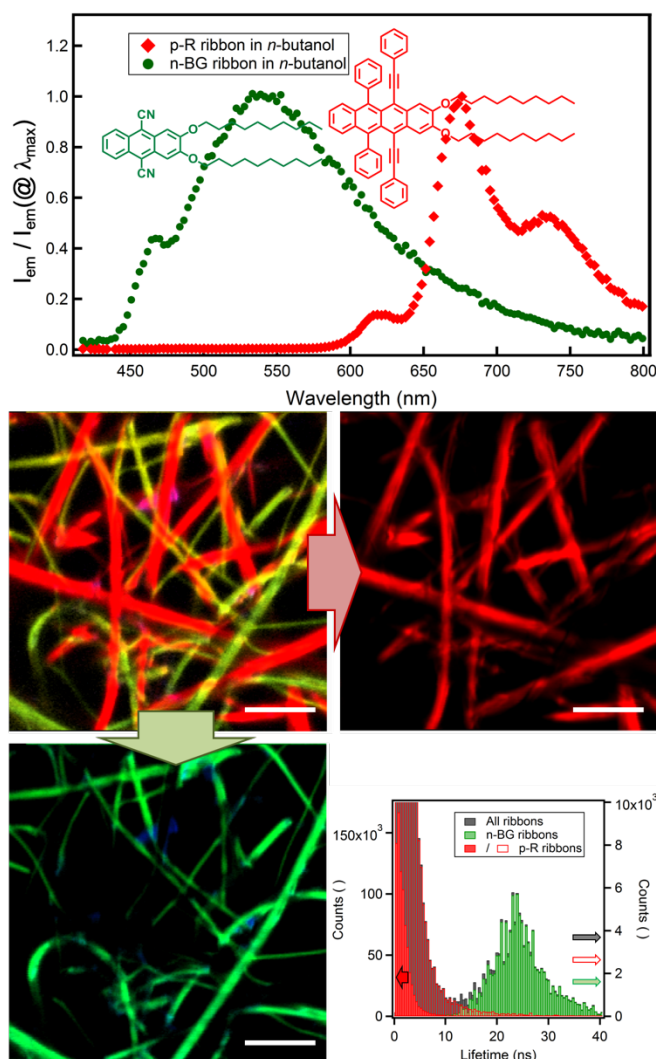

**Figure 1.** a) Molecular structures of **n-BG** (green) and **p-R** (red) and relative emission intensity spectra  $I_{em}/I_{em}(@\lambda_{max})$  of the two different nanoribbons in *n*-butanol. b) Hyperspectral image: the emission spectrum of each pixel is converted into the corresponding RGB-color,  $\lambda_{ex} = 375$  nm. The spectra in a) are obtained from individual ribbons from this map. c) Digital bandpass filter (650 nm - 780 nm) applied on b) highlighting the ribbons attributed to **p-R**. d) Digital bandpass filter (405 nm - 550 nm) applied on b) showing the ribbons attributed to **n-BG**. (Scale bar: 5  $\mu\text{m}$ ). Note: some blue emissive spots can be attributed to photo-oxidized **p-R** (see S.I.). e) Fluorescence lifetime distribution of the same area: the longer lifetimes are correlated to the green-emissive, and the shorter to the red-emissive ribbons.

a Lippert-Mataga analysis (Figure S1).<sup>37</sup> The tetracene **p-R** emits very efficiently in the red spectral region, showing weak solvatochromism (Tables 1, S1, Figure S2). As compared to the tetraphenyl (rubrene) analogue,<sup>35</sup> the extension of the conjugation through the aryls results in red-shifted absorption and emission by  $\sim 50$  nm, with a  $2.5\times$  larger extinction coefficient and a  $1.7\times$  larger radiative constant due to an increased oscillator strength (value calculated by Strickler-Berg relation<sup>38</sup> matches experimental value, Table S1).

**n-BG** and **p-R** are dissolved at high temperature ( $T > 80$  °C) in *n*-butanol, DMSO or a mixture thereof (both 2.0 mM in 1 mL) and cooled down to room temperature (22-23 °C) to induce self-assembly. Microscopy (HS-CFM) provides the fluorescence spectrum (spectral resolution  $\Delta\lambda < 3$  nm) for each pixel and was therefore used to characterize the orthogonality of the self-assembly with optical diffraction limited spatial resolution. The

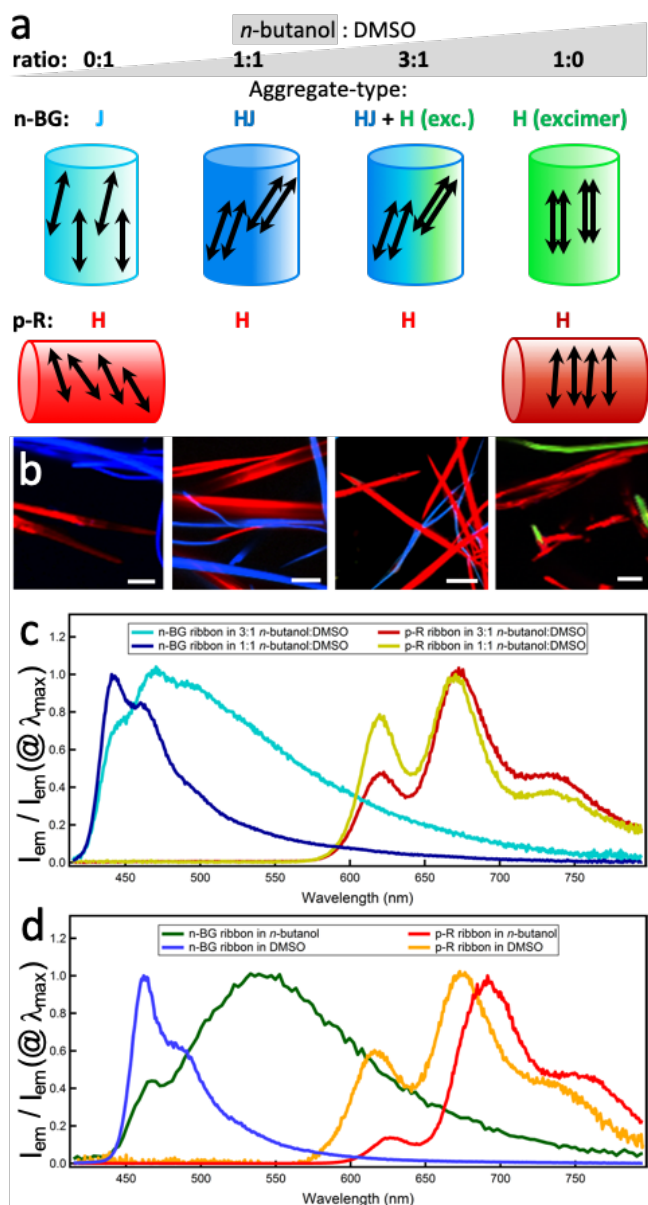


**Figure 2.** a) Solvent mixtures for **a**) and **b**). Attributions of the main emission features to the aggregate types and simplified representation of possible packing within a ribbon of four molecules (each represented by the emission dipole oriented along the short axis of the *n*-acene, additional symmetry is probable). **b**) Hyperspectral images of self-sorted ribbons in the four solvent conditions. Red-emissive ribbons are attributed to **p-R**, the other to **n-BG** (Scale bars: 5  $\mu\text{m}$ ). **c**) and **d**) Relative emission intensity spectra of each ribbon type in the four solvents conditions; spectral data taken from the ribbons of the hyperspectral images **b**).  $\lambda_{\text{exc}} = 375 \text{ nm}$ .

typically  $40 \times 40 \mu\text{m}$  images allow to easily visualize the distribution of the molecules since for each pixel the spectra are converted into RGB colour code. Figures 1b-e clearly show that two sets of nanoribbons form in *n*-butanol, emitting with a narrow distribution of distinguishable colours (see CIE graph in Figure S4). The green- and red-emitting ribbons are attributed to **n-BG** and **p-R**, respectively. A spectral filtering highlights each set of objects (Figures 1c,d), showing that they are constituted of continuous nanoribbons of similar size and aspect ratio, 200–1500 nm wide (bundles can form). The spectral shifts, as compared to solution, are typically observed for self-assembly of *n*-acenes and are discussed below. In addition, the two

ribbon-sets emit with very different fluorescence decay times (distributions at  $23.6 \pm 6.2 \text{ ns}$  and  $0.9 \pm 0.7 \text{ ns}$  for **n-BG** and **p-R**, respectively), as shown by fluorescence lifetime imaging microscopy (FLIM, Figures 1e, S5), a technique also previously used to differentiate orthogonal self-assembly.<sup>5</sup> HS-CFM further reveals that the emission of the **n-BG** ribbons does not contain measurable contribution of structured red emission (Figure 1a). This demonstrates that the **n-BG** ribbons are not contaminated by **p-R**. Indeed, previous studies on similar nano-ribbons or -fibres have shown that even small amounts of dopants ( $\sim 0.5\%$  mol equivalents), in this case **p-R**, would act as efficient acceptors in an energy transfer process (Figure S4b) and emit significantly.<sup>35,39–42</sup> Approximately similar amounts of green and red ribbons are typically observed, the red ribbons being attributed to **p-R**. These do not present any measurable **n-BG** emission under UV excitation, and comparison with previous studies also suggests that if present in large amounts, residual emission of unquenched **n-BG** should be observed. Whereas the presence of small amounts of **n-BG**, quenched by energy transfer, in **p-R** ribbons cannot be completely excluded, it crucially shows no impact on fluorescence properties. This constitutes thereby a significant case of quantitative narcissistic self-sorting of **n-BG** and **p-R**, a case without H-bonds, only sporadically described in the literature.

To get further insight on the dynamics of the orthogonal self-assembly, each type of nanoribbon's growth was discriminated in two spectral ranges and followed by simultaneous imaging using fluorescence video-microscopy. In pure *n*-butanol, the ribbons grow and ripen within minutes, the red emissive **p-R** ribbons ( $\lambda_{\text{detection}} > 720 \text{ nm}$ ) being ripe slightly before the **n-BG** ribbons ( $\lambda_{\text{detection}}$ : 510–550 nm). Changing to dimethylsulfoxide (DMSO), a non-protic solvent with similar polarity but larger permanent dipole ( $E_{\text{T}}(\text{BM})_{\text{DMSO}} = 50.3$  vs.  $E_{\text{T}}(\text{BM})_{\text{BuOH}} = 53.6$ ,  $\mu_{\text{DMSO}} = 3.96$  vs.  $\mu_{\text{but}} = 1.66$ ),<sup>43,44</sup> the time necessary to obtain ripe red ribbons increases to several tens of minutes and the ripening order is inverted. Mixing the two solvents induces intermediate growth speeds, and thereby ripe **n-BG** and **p-R** ribbons are obtained after a similar time in a 3:1 *n*-butanol:DMSO blend (the onset of nucleation could not be observed due to a lack of contrast of brightness). In all cases, both sets of ribbons grow orthogonally, suggesting that the self-sorting mechanism does not rely on differences of growth kinetics.

The molecular packing determines the emission colours and affects the charge mobility in the solid state, and can be deduced from the spectral properties.<sup>45</sup> In the case of **n-BG**, the emission spectra of the ribbons significantly change with the solvent, and can be attributed to the appearance of dipolar couplings related to the molecular packing.<sup>34,36</sup> In these ribbons, it has to be taken into account that several emissive states can be present, and that the lower energy state can be due to packing defects acting as energy traps populated by Förster type resonance energy transfer (FRET).<sup>34,41</sup> In pure *n*-butanol, the emission is mostly constituted of a long-lived broad excimer-like emission at 545 nm (Figure 2d), attributed to co-planar stacked **n-BG** molecules (same geometry as a "H-type" aggregate, Figure 2a).<sup>37,46</sup> This excimer emits with a typical reduced radiative

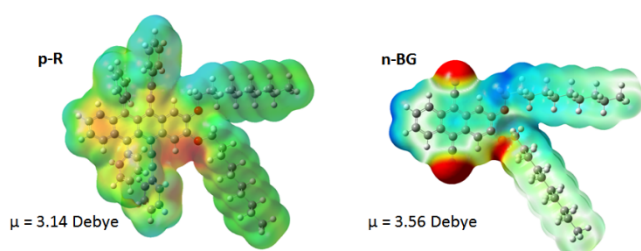

**Figure 3.** Calculated charge density of **p-R** and **n-BG** in *n*-butanol solution of meta-stable asymmetric conformers, obtained by energy minimization upon rotation of the C(ar)-O-C-C(alk) torsional angle (9 steps of 20°). Both molecules display a large dipolar moment of 3.46 and 4.11 Debye, respectively.

constant<sup>47</sup> and lifetimes much longer than those observed for the ICT state emission in solution (Tables 1, S2), although possibly displaying a CT-character.<sup>48</sup> The non-radiative processes are also slowed down due to restrictions of deactivation through conformational relaxation. With progressive increase of DMSO proportion, this excimer band decreases (3:1 mix) and disappears (1:1 mix) in favour of a structured monomer-like emission at 442 nm, weakly shifted compared to that observed in an apolar solvent. This contrasts with the more pronounced red-shifted structured emission in pure DMSO ( $\lambda_{\text{max}} = 462$  nm for the 0-0 band). The latter shift is typically attributed to J-type dipolar coupling of slip-stacked **n-BG** molecules.<sup>49</sup> The strong attenuation of the shift of the 442 nm emission band could be attributed to a combination of couplings leading to HJ-aggregates (or “null” aggregates).<sup>50</sup> In this cases, J-type coulombic long distance coupling is compensated by CT-mediated short-distance H-type coupling.<sup>50</sup> In summary, the change of the molecular packing and thus aggregate-type progresses from “J” to “HJ”, “H”+“HJ”, and “H”, respectively, from DMSO to *n*-butanol (Figure 2a). This is supported by emission polarization microscopy, which shows that the excimer-like emission is remarkably highly polarized along the ribbons’ long axis ( $P_{\text{max}} > 0.7$ , Figures S5b,f). Considering this large value, and rare previous studies,<sup>51–54</sup> it can be assumed tentatively that the excimer emission polarization has a main component oriented parallel to the average orientation of the transition dipoles of the two monomers, along the short axis of the *n*-acene, and minor components along the long molecular axis and/or normal to the molecular planes. Thus, the short axis of the anthracene cores of the excimer molecular pairs essentially point towards the ribbons’ long axis (Figure 2a). The J-coupled molecules also emit with a polarization oriented along the short axis. The lower  $P_{\text{max}}$  values ( $0.15 < P_{\text{max}} < 0.5$ , Figures S5c,f) can be due to an polarization component along the long axis of the ribbon, resulting from the angle between the axes of coupled molecules and the dipolar J-coupling along that axis.<sup>45</sup>


The spectral changes observed for **p-R** emission are also indicative of coulombic dipolar coupling, and due to a larger oscillator strength, these may dominate over CT-mediated coupling. Indeed, a blue-shift and a lower energy tail appear in the absorption (see Figure S2a). It is reasonably assumed that this tail does not majorly affect the emission at  $619 \pm 4$  nm by emission-reabsorption, and that all the bands are resulting from only one emissive state. The red-shift of the emission in the ribbons relative to solution could be attributed to stabilization of the excited state in a more polar environment, created by the large dipoles of distorted conformers (see below and previous studies<sup>34</sup>). This is more pronounced in *n*-butanol, the emission of the 0-1 band being further red-shifted by 19 nm.

Although a red-shift is often attributed to J-aggregates, in which 0-0 emission band is usually the highest, the absorption features and the significantly lower intensity of the 0-0 band emission (600-650 nm) relative to the 0-1 band (at 650-700 nm) rather suggest H-type aggregates which emit due to local disorder-induced symmetry-breaking.<sup>55</sup> In *n*-butanol, the weakness of the 0-0 band is also in agreement with partially disordered H-aggregates with a larger coupling correlation length.<sup>56</sup> The main polarization component of the 0-1 band emission is essentially oriented perpendicular to the long axis of the ribbons (Figures 2a, S5, S6), indicating the same orientation for the tetracene short axis. The 0-0 band, although only weak in *n*-butanol, shows a different orientation, in agreement with the expectation to be perpendicular to the 0-1 case and reflect the direction of the chain of coherent dipoles (out-of-plane contributions could be at the origin of attenuated polarization values). The H-type molecular packing is likely to promote charge mobility, necessary for electro-luminescence (see below).

In addition to aromatic core interactions and phase separation of aromatics and alkyl chains at the molecular scale,<sup>34</sup> directional self-assembly in ribbons in the absence of H-bonds can be dominated by dipole-dipole interactions.<sup>57</sup> Recent work on 9,10-disubstituted anthracene nanoribbons unravelled the contribution in the anisotropic growth mechanism of dipole-dipole interactions originating from thermally-activated asymmetric conformers.<sup>34</sup> Therefore, by analogy, the same type of conformers of **p-R** and **n-BG** were studied by theoretical calculations using DFT (density functional theory) (Figures 3, S8). Although the most stable conformer is symmetric with a moderate dipole (1.22 D and 1.93 D for **p-R** and **n-BG**, respectively, Table S3), in a higher energy meta-stable conformer with an asymmetric conformation of the alkyl-chains, a larger dipole moment can be formed mostly located on the aryl(-O-CH<sub>2</sub>-)<sub>2</sub> area of the molecule (Figure 3). For **p-R**, the dipole  $\mu_{\text{p-R}}$  can reach 3.46 Debye. **n-BG** displays however a more complex charge distribution. Indeed, not only can the asymmetry-induced dipole moment reach  $\mu_{\text{n-BG}} = 4.11$  Debye, but additionally, the electron-withdrawing cyano groups contribute with strong dipoles ( $\mu_{\text{CN}} \sim 3.5$  Debye)<sup>58</sup> and lead to an approximately quadrupolar character of the molecule. The observed polymorphism of the ribbons could be related to the solvent-dependent stabilization of the asymmetric conformers, in solution (~1.5-2.5% of population, Table S3), but also in the nuclei and in the final ribbon (population up to ~100%)<sup>34</sup>. This would influence thereby self-assembly kinetics, the final packing geometry (Table S3), but also the increased polarity of the micro-environment in the ribbon<sup>34</sup> and related stabilization of CT-character and red-shift of emission. A finer understanding of this interplay would certainly prove of interest in the field of organic opto-electronics with an ever-growing interest in excited states displaying a CT-character.

Concerning the origin of the self-sorting, one of the most remarkable differences between **n-BG** and **p-R** resides thus in the fact that **n-BG** has a strong quadrupolar character. Indeed, thermodynamic parameters determining nucleation and growth kinetics have been levelled out in the solvent mixture 3:1. In addition, no specific binding functions are present, such

as H-bond donor or acceptor, or apolar / polar side-chains.<sup>59</sup> Another explanation could be related to the size of the molecules or of crystallographic unit cells. As previously shown, a blending of two components can be favoured by the match of their respective crystallographic unit cells.<sup>60</sup> A mismatch could inhibit the blending of nanoaggregates of **n-BG** and **p-R** during the growth, possibly involving the oriented-attachment mechanism proposed recently for similar nanoribbons.<sup>34</sup> At the molecular level, steric hindrance could also lead to self-sorting, but it was shown that DDOA, a molecule with a size comparable to **n-BG**, and the bulkier **p-R** blend into mixed nanoobjects (Figure S7). Similarly, **p-R** does not self-sort with a 9,10-diphenylethynyl-anthracene<sup>36</sup> analogue (Figure S7), and forms mixed nanoribbons. Therefore, this work suggests that the mismatch of dipolar and quadrupolar character of **n-BG** and **p-R**, respectively, plays an essential role in the exclusive narcissistic self-sorting.

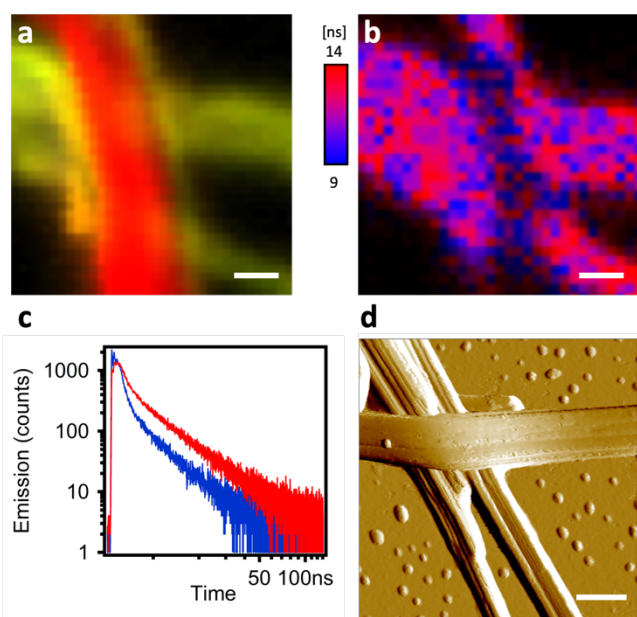


**Figure 4.** a) Hyperspectral image of a **n-BG/p-R** ribbon p-n-junction grown in *n*-butanol (scale bars: 500 nm). b) FLIM (average fluorescence lifetime) image using a 510/80 bandpass filter to retain **n-BG** emission only. c) Decays of **n-BG** emission of an isolated ribbon (red curve) and of the junction in (b) (blue curve). Red decay tri-exponential fit (lifetime  $\tau$  and amplitude thereof  $A$ ):  $\tau_1 = 0.6$  ns ( $A_1 = 21\%$ ),  $\tau_2 = 3.4$  ns ( $A_2 = 60\%$ ),  $\tau_3 = 15.9$  ns ( $A_3 = 19\%$ ); blue decay:  $\tau_1 = 0.3$  ns ( $A_1 = 16\%$ ),  $\tau_2 = 1.9$  ns ( $A_2 = 63\%$ ),  $\tau_3 = 10.2$  ns ( $A_3 = 21\%$ ).  $\lambda_{\text{ex}} = 375$  nm. d) AFM amplitude image of a p-n-junction grown in *n*-butanol, deposited and dried on a glass cover slip. The “horizontal” ribbon is **n-BG**, and the “vertical” ribbon is **p-R**.

### p-n Junctions

The interfacial interactions between self-sorted ribbons were emphasized by two experiments: inter-ribbon energy transfer and p-n junction electroluminescence. In the first case, the p-n junctions were studied by HS-CFM and FLIM (Figure 4). The spectral overlap of **n-BG** emission and **p-R** absorption (Figure S4) is ideal for excitation energy transfer (ET) by either resonant (Förster: FRET) or electron exchange (Dexter) mechanism, or trivial emission-reabsorption. Emission intensity studies do not clearly reveal the ET, mostly because the emission of the acceptor **p-R** resulting from direct excitation cannot be avoided and overwhelms the variations in intensities. However, FLIM performed in the green spectral region (470–550 nm) reveals

that the average decay-time of **n-BG** emission drops at a junction from 5.24 ns to 3.38 ns, corresponding to 35% of quenching (Figures 4b,c). Decay times are intensity-independent, and change only if ET occurs (not for emission-reabsorption). This significant quenching of **n-BG** can be attributed to ET, most probably by FRET mechanism which can occur between singlet states at contact and at nanometric distances. Since this ribbon-to-ribbon ET occurs efficiently even though the ribbons are at least tens of nm thick, it can be proposed that an efficient exciton hopping, *i.e.* homo-ET, occurs within the ribbons. To the best of our knowledge this constitutes a rare case of efficient optical communication at junctions of nanofibers or ribbons of this size through ET mechanisms, and could be interesting for the development of photonic elements.<sup>61–63</sup>

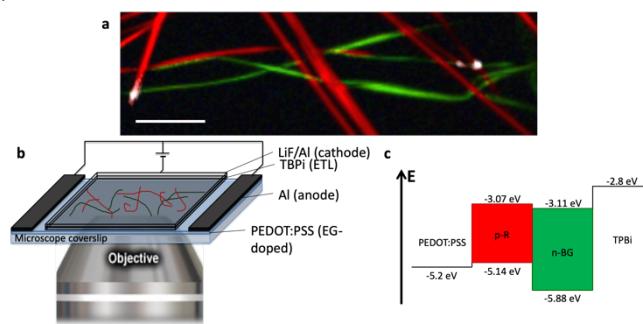

**Figure 5.** a) Overlaid images of emission of self-sorted ribbons in a device, (red and green) fluorescence hyperspectral and (white) electroluminescence intensity at certain p-n-junctions ( $\lambda_{\text{em}} > 405$  nm, see also SI, scale bar: 10  $\mu\text{m}$ ). b) Scheme of the device, placed on a microscope objective. c) energy level diagram of the EL-device.

A remarkable ‘light ON’-switching occurs at the p-n-junctions in an electroluminescent device (Figure 5). Self-sorted **n-BG** and **p-R** ribbons grown in *n*-butanol are spin-coated on an ethylene glycol treated PEDOT:PSS thin-film, acting as hole-transport and hole-injection layer, and dried. The ITO-free, non-optimized electroluminescent device was completed with the electron-injection and electron-transport layer TBPI (2,2',2''-(1,3,5-benzinetriyl)-tris(1-phenyl-1-H-benzimidazole)), and an Li/Al cathode, both evaporated on top of the ribbons according to published procedures.<sup>64,65</sup> Fluorescence microscopy correlated with HS-CFM demonstrated that electro-luminescence (EL) was generated at some p-n junctions (Figure 5, S10), whereas isolated ribbons do not emit. EL demonstrates charge transport in both ribbons, **n-BG** acting as electron transporting n-type and **p-R** as hole transporting p-type semiconductors, respectively. The absence of EL from certain junctions could be due to an inappropriate order of the successive layers (inversion of **n-BG** and **p-R** relative to that shown in Figure 5c), or an excessive thickness of certain ribbons and resulting insufficient charge transport. The anisotropic shape of the emissive spots and their orientation (Figure S10) could be related to some exciton hopping or waveguiding along the **p-R** ribbons, attributing thus the EL to **p-R**, although insufficient photons are emitted per spot to obtain a spectrum. Cyclic voltammetry of **n-BG** and **p-R** in solution show that hole injection from PEDOT:PSS could be possible into **p-R**, but not **n-BG** (Figures 5c, S9). In contrast, electron injection from TBPI could occur into both **n-BG** and **p-R**. The rarely observed and very weak EL from some isolated **p-**

**R** ribbons (Figure S11) suggests that electron injection is inefficient. Therefore, the combination of **n-BG** and **p-R** in p-n junction is required herein to transport both holes and electrons, with a recombination that can only occur in **p-R** due to an energy gap between the HOMO levels of **p-R** and **n-BG** that cannot be overcome. EL also demonstrates that self-sorting allows interfacial interactions that are sufficiently intimate for electron injection to occur from **n-BG** ribbons into **p-R** ribbons and charge recombination therein. The necessity of p-n junction is not a requisite for EL of organic nanoobjects,<sup>64,65</sup> but this allows to have an EL switch-on at specific sites in an interpenetrated network. In perspective, p-n junctions in hierarchically organized and patterned nanoribbon electroluminescent devices could be of interest. The methodology developed for the photo-induced hierarchical self-assembly and patterning recently demonstrated for anthracene nanofibers<sup>33</sup> could be useful. In addition, EL of **p-R** could be expected to be significantly linearly polarized (photoluminescence P value can reach ~0.5), an important feature for EL-devices such as OLEDs.

## Conclusions

In conclusion, narcissistic self-sorting can be obtained for two polyaromatic molecules substituted with the same side-chains, without involving **neither** H-bonds nor differences in the self-assembly kinetics. The contrast of quadrupolar and dipolar character of **n-BG** and **p-R**, respectively, is proposed to contribute significantly to the self-sorting. Favourably interfaced p-n junctions are nevertheless obtained, leading to inter-ribbon FRET and electro-luminescence switch-on at the junctions.

## Experimental

All methods are described in more details in the Supplementary Information.

The nanoribbons samples were prepared by mixing 2 mM of both **n-BG** and **p-R** in 1 ml of *n*-butanol or DMSO, or mixture thereof, at r.t., then heated at least at 80°C in the dark with continuous N<sub>2</sub> purging, and finally left at 22°C to allow cooling down. Pristine nanoribbon dispersions were used for bulk spectroscopic measurements. However, the optical density of the **p-R** nanoribbon dispersion was not appropriate for an accurate quantum yield measurement, and addition of solvent, to reduce the density, lead to partial dissolution of the ribbons. Pristine **n-BG** nanoribbons were obtained by the injection method, and the final solvent composition included *n*-butanol and dichloromethane. In order to perform microscopy studies, the nanoribbon dispersions were drop-casted or spin-coated on standard microscopy glass coverslips, dried, and placed under gentle N<sub>2</sub> flow. For electroluminescence experiments, the nanoribbons were spin-coated onto the solvent post-treated PEDOT:PSS layer, and dried. The electron transport layer TBPI is thermally evaporated under vacuum, and bilayer cathodes of lithium fluoride and Al are then evaporated through a shadow mask. The

voltage sweeps are driven manually (15 V max) until luminescence is observed by the CCD-camera under microscopy.

Confocal fluorescence microscopy was realized on a Picoquant Microtime 200 (polarization, FLIM and HS-CFM). Due to wavelength dependence of the two SPAD detectors used for polarization microscopy, the G-factor was measured for several narrow spectral regions applying bandpass filters (455 - 480 nm, 510 - 550 nm, 608 - 650 nm) and a 720 long-pass filter on a broadband emissive dilute dyes solution.  $I_{//}$  and  $I_{\perp}$  are the intensities of the components of the fluorescence emission parallel and perpendicular, respectively, to the polarization of the excitation beam. The polarization P of each pixel is given by  $P = (I_{//} - G \times I_{\perp}) / (I_{//} + G \times I_{\perp})$ . P varies with the orientation of the long axis of the ribbon, between -1 and +1, and therefore  $P_{\max}$  corresponds to the highest value of |P| measured for a straight section of the ribbons. For HS-CFM hyperspectral imaging the emission light was detected by an Andor SR300i spectrometer equipped with a Newton EMCCD. A high resolution spectrum was taken, with a 6 ms/pixel scan, for each pixel and then converted into CIE coordinates and RGB-colors. The emission spectra were intensity corrected by using an ARGOLIGHT calibration slide. The same microscope was used to measure electroluminescence through a Hamamatsu video CCD camera, and therefore superposition with HS-CFM was possible on the same sample area.

## Author Contributions

P.S.: conceptualization, spectroscopy, microscopy, writing. C.d.V.: synthesis. L.G.-R. spectroscopy, theoretical studies. G.R. microscopy, software. M.-T.K. spectroscopy. C.S. synthesis. L.R. and B.P. anodes for EL. Y.-T.T., L.H. and D.B. cathodes, expertise and funding for EL. A.D.G. conceptualization, supervision, data analysis, writing, funding.

## Conflicts of interest

"There are no conflicts to declare".

## Acknowledgements

The authors acknowledge the financial support of the European Research Council Marie Curie Actions (FP7-PEOPLE-2012-ITN SMARTNET Grant agreement Nr 316656); the CNRS; the French Ministry of Education and Research; the Région Aquitaine; the ANR-06-JCJC-0030; the Department of Education, Science and Universities of the Basque Country Government (postdoctoral grant and project IT1639-22); the "Arina" informatic cluster of UPV/EHU; the facilities ELORGA of UB; and the ANR-13-IS07-0001 EVOLVE. The authors thank Dr. A. Mendez-Ardoy for the CV measurements and CESAMO for structural analyses (ISM, Univ. Bordeaux).

## Notes and references

- 1 X. Y. Hu, T. Xiao, C. Lin, F. Huang and L. Wang, *Acc. Chem. Res.*, 2014, **47**, 2041–2051.
- 2 A. Pal, S. Karthikeyan and R. P. Sijbesma, *J. Am. Chem. Soc.*, 2010, **132**, 7842–7843.

- 3 N. Hosono, M. A. J. Gillissen, Y. Li, S. S. Sheiko, A. R. A. Palmans and E. W. Meijer, *J. Am. Chem. Soc.*, 2013, **135**, 501–510.
- 4 Y.-C. Yeh, R. Tang, R. Mout, Y. Jeong and V. M. Rotello, *Angew. Chemie Int. Ed.*, 2014, **53**, 5137–5141.
- 5 J. Boekhoven, A. M. Brizard, M. C. A. Stuart, L. Florusse, G. Raffy, A. Del Guerzo and J. H. van Esch, *Chem. Sci.*, 2016, **7**, 6021–6031.
- 6 H. Sato, Y. Miura, N. Saito, K. Kobayashi and O. Takai, *Biomacromolecules*, 2007, **8**, 753–756.
- 7 N. C. Wickremasinghe, V. A. Kumar and J. D. Hartgerink, *Biomacromolecules*, 2014, **15**, 3587–3595.
- 8 K. Jakab, C. Norotte, F. Marga, K. Murphy, G. Vunjak-Novakovic and G. Forgacs, *Biofabrication*, 2010, **2**, 1–14.
- 9 T. J. Gardner, C. D. Frisbie and M. S. Wrighton, *J. Am. Chem. Soc.*, 1995, **117**, 6927–6933.
- 10 B. R. Walker, R. A. Wassel, D. M. Ștefanescu and C. B. Gorman, *J. Am. Chem. Soc.*, 2004, **126**, 16330–16331.
- 11 H. Xu, R. Hong, T. Lu, O. Uzun and V. M. Rotello, *J. Am. Chem. Soc.*, 2006, **128**, 3162–3163.
- 12 J. van Herrikhuyzen, A. Syamakumari, A. P. H. J. Schenning and E. W. Meijer, *J. Am. Chem. Soc.*, 2004, **126**, 10021–10027.
- 13 Y. Zhang, H. Dong, Q. Tang, S. Ferdous, F. Liu, S. C. B. Mannsfeld, W. Hu and A. L. Briseno, *J. Am. Chem. Soc.*, 2010, **132**, 11580–11584.
- 14 K. Sugiyasu, S. Kawano, N. Fujita and S. Shinkai, *Chem. Mater.*, 2008, **20**, 2863–2865.
- 15 A. Heeres, C. van der Pol, M. Stuart, A. Friggeri, B. L. Feringa and J. van Esch, *J. Am. Chem. Soc.*, 2003, **125**, 14252–14253.
- 16 P. E. Laibnis, J. J. Hickman, M. S. Wrighton and G. M. Whitesides, *Science (80-. )*, 1989, **245**, 845–847.
- 17 A. M. Johnson, C. A. Wiley, M. C. Young, X. Zhang, Y. Lyon, R. R. Julian and R. J. Hooley, *Angew. Chemie - Int. Ed.*, 2015, **54**, 5641–5645.
- 18 Z. He, W. Jiang and C. A. Schalley, *Chem. Soc. Rev.*, 2015, **44**, 779–789.
- 19 M. R. Molla, A. Das and S. Ghosh, *Chem. - A Eur. J.*, 2010, **16**, 10084–10093.
- 20 Y. T. Tsai, G. Raffy, H. F. Liu, B. J. Peng, K. P. Tseng, L. Hirsch, A. Del Guerzo, D. M. Bassani and K. T. Wong, *Mater. Chem. Front.*, 2020, **4**, 845–850.
- 21 R. Kubota, S. Liu, H. Shigemitsu, K. Nakamura, W. Tanaka, M. Ikeda and I. Hamachi, *Bioconjug. Chem.*, 2018, **29**, 2058–2067.
- 22 S. Onogi, H. Shigemitsu, T. Yoshii, T. Tanida, M. Ikeda, R. Kubota and I. Hamachi, *Nat. Chem.*, 2016, **8**, 743–752.
- 23 M. M. Safont-Sempere, G. Fernández and F. Würthner, *Chem. Rev.*, 2011, **111**, 5784–5814.
- 24 F. Würthner, C. Bauer, V. Stepanenko and S. Yagai, *Adv. Mater.*, 2008, **20**, 1695–1698.
- 25 S. Prasanthkumar, S. Ghosh, V. C. Nair, A. Saeki, S. Seki and A. Ajayaghosh, *Angew. Chemie - Int. Ed.*, 2015, **54**, 946–950.
- 26 N. Fujita, S. Shinkai and R. V. January, *Chem. Mater.*, 2008, **20**, 3871–3873.
- 27 D. K. Kumar and J. W. Steed, *Chem. Soc. Rev.*, 2014, **43**, 2080–2088.
- 28 K. L. Morris, L. Chen, J. Raeburn, O. R. Sellick, P. Cotanda, A. Paul, P. C. Griffiths, S. M. King, R. K. O'Reilly, L. C. Serpell and D. J. Adams, *Nat Commun*, 2013, **4**, 1480.
- 29 E. R. Cross, S. Sproules, R. Schweins, E. R. Draper and D. J. Adams, *J. Am. Chem. Soc.*, 2018, **140**, 8667–8670.
- 30 D. Genovese, A. Aliprandi, E. A. Prasetyanto, M. Mauro, M. Hirtz, H. Fuchs, Y. Fujita, H. Uji-I, S. Lebedkin, M. Kappes and L. De Cola, *Adv. Funct. Mater.*, 2016, **26**, 5271–5278.
- 31 E. R. Draper and D. J. Adams, *Chem. Soc. Rev.*, 2018, **47**, 3395–3405.
- 32 T. Brotin, R. Utermohlen, F. Fages, H. Bouas-Laurent and J.-P. Desvergne, *J. Chem. Soc. Chem. Commun.*, 1991, 416–418.
- 33 C. de Vet, L. Gartzia-Rivero, P. Schäfer, G. Raffy and A. Del Guerzo, *Small*, 2020, **16**, 1906723.
- 34 P. Schäfer, L. Gartzia-Rivero, M. T. Kao, C. Schäfer, S. Massip, C. De Vet, G. Raffy and A. Del Guerzo, *J. Mater. Chem. C*, 2021, **9**, 136–147.
- 35 C. Giansante, G. Raffy, C. Schäfer, H. Rahma, M. T. Kao, A. G. L. Olive and A. Del Guerzo, *J. Am. Chem. Soc.*, 2011, **133**, 316–325.
- 36 M. T. Kao, C. Schäfer, G. Raffy and A. Del Guerzo, *Photochem. Photobiol. Sci.*, 2012, **11**, 1730–1736.
- 37 A. F. Olea, D. R. Worrall, F. Wilkinson, S. L. Williams and A. Abdel-Shafi, *Phys. Chem. Chem. Phys.*, 2002, **4**, 161–167.
- 38 S. J. Strickler and R. A. Berg, *J. Chem. Phys.*, 1962, **37**, 814–822.
- 39 A. Ajayaghosh, V. K. Praveen and C. Vijayakumar, *Chem. Soc. Rev.*, 2008, **37**, 109–122.
- 40 A. G. L. Olive, A. Del Guerzo, C. Schäfer, C. Belin, G. Raffy and C. Giansante, *J. Phys. Chem. C*, 2010, **114**, 10410–10416.
- 41 C. Giansante, C. Schäfer, G. Raffy and A. Del Guerzo, *J. Phys. Chem. C*, 2012, **116**, 21706–21716.
- 42 A. Del Guerzo, A. G. L. Olive, J. Reichwagen, H. Hopf and J. P. Desvergne, *J. Am. Chem. Soc.*, 2005, **127**, 17984–17985.
- 43 M. A. d. R. Silva, D. C. Da Silva, V. G. Machado, E. Longhinotti and V. L. A. Frescura, *J. Phys. Chem. A*, 2002, **106**, 8820–8826.
- 44 D. C. Da Silva, I. Ricken, M. A. D. R. Silva and V. G. Machado, *J. Phys. Org. Chem.*, 2002, **15**, 420–427.
- 45 N. J. Hestand and F. C. Spano, *Chem. Rev.*, 2018, **118**, 7069–7163.
- 46 S. Samanta, S. K. Ray, S. Deolka, S. Saha, P. K. R., R. Bhowal, N. Ghosh and D. Chaudhuri, *Chem. Sci.*, 2020, **11**, 5710–5715.
- 47 H. Liu, L. Yao, B. Li, X. Chen, Y. Gao, S. Zhang, W. Li, P. Lu, B. Yang and Y. Ma, *Chem. Commun.*, 2016, **52**, 7356–7359.
- 48 M. S. Myong, J. Zhou, R. M. Young and M. R. Wasielewski, *J. Phys. Chem. C*, 2020, **124**, 4369–4377.
- 49 J. Xiao, Z. Yin, B. Yang, Y. Liu, L. Ji, J. Guo, L. Huang, X. Liu, Q. Yan, H. Zhang and Q. Zhang, *Nanoscale*, 2011, **3**, 4720–4723.
- 50 N. J. Hestand and F. C. Spano, *J. Chem. Phys.*, 2015, **143**, 244707.



- 51 R. L. Barnes and J. B. Birks, *Proc. R. Soc. London. Ser. A. Math. Phys. Sci.*, 1966, **291**, 570–582.
- 52 J. Tanaka and M. Shibata, *Bull. Chem. Soc.*, 1968, **41**, 34–41.
- 53 R. M. Hochstrasser and A. Malliaris, *J. Chem. Phys.*, 1965, **42**, 2243–2244.
- 54 B. Lu, X. Fang and D. Yan, *ACS Appl. Mater. Interfaces*, 2020, **12**, 31940–31951.
- 55 F. C. Spano, *Acc. Chem. Res.*, 2010, **43**, 429–439.
- 56 F. C. Spano, *J. Chem. Phys.*, 2005, **122**, 234701.
- 57 X. X. Zhang, X. X. Zhang, K. Zou, C.-S. S. Lee and S.-T. T. Lee, *J. Am. Chem. Soc.*, 2007, **129**, 3527–3532.
- 58 H. S. Nalwa and S. Miyata, *Nonlinear optics of organic molecules and polymers*, CRC Press, 1997.
- 59 M. J. Mayoral, C. Rest, J. Schellheimer, V. Stepanenko and G. Fernández, *Chem. - A Eur. J.*, 2012, **18**, 15607–15611.
- 60 S. Banerjee, R. K. Das, P. Terech, A. De Geyer, C. Aymonier, A. Loppinet-Serani, G. Raffy, U. Maitra, A. Del Guerso and J. P. Desvergne, *J. Mater. Chem. C*, 2013, **1**, 3305–3316.
- 61 C. Zhang, Y. Yan, Y. S. Zhao and J. Yao, *Acc. Chem. Res.*, 2014, **47**, 3448–3458.
- 62 Y. Yan, C. Zhang, J. Yao and Y. S. Zhao, *Adv. Mater.*, 2013, **25**, 3627–3638.
- 63 A. Camposeo, D. B. Granger, S. R. Parkin, D. Altamura, C. Giannini, J. E. Anthony and D. Pisignano, *Chem. Mater.*, 2019, **31**, 1775–1783.
- 64 K. P. Tseng, F. C. Fang, J. J. Shyue, K. T. Wong, G. Raffy, A. Del Guerso and D. M. Bassani, *Angew. Chemie - Int. Ed.*, 2011, **50**, 7032–7036.
- 65 Y.-T. Tsai, K.-P. Tseng, Y.-F. Chen, C.-C. Wu, G.-L. Fan, K.-T. Wong, G. Wantz, L. Hirsch, G. Raffy, A. Del Guerso and D. M. Bassani, *ACS Nano*, 2016, **10**, 998–1006.